

# Article Info

Received: 25 Jul 2014 | Revised Submission: 10 Aug 2014 | Accepted: 20 Aug 2014 | Available Online: 15 Sept 2014

## Experimental Analysis and Modeling of MRR in Electrical Discharge Machining

Ranganath M. S.\*, Vipin\*, Manoj Kumar Singh\*\* and Jitender Kumar\*\*\*

### ABSTRACT

The selection of machining parameters is one of the most important aspects in the electrical discharge machining operation as these conditions has important effect on material removal rate (MRR). In this paper the experiments were conducted on the machining of EN 31 die steel with graphite electrode with electrical discharge machining (EDM). The EDM oil commercial grade has been used as dielectric fluid. The effect of various EDM parameters such as discharge current, Ton and Toff has been investigated to yield the response in terms of MRR. In this work mathematical models have been developed for relating the MRR with machining parameters like discharge current, Ton, and Toff. The optimum value has been determined with the help of main effect plot and ANOVA table.

**Keywords:** Electrical Discharge Machining (EDM); Mathematical Modeling; Material Removal Rate (MRR); ANOVA; EN 31 die Steel; Graphite Electrode.

### 1.0 Introduction

Electric discharge machining (EDM), sometimes also referred to as spark machining, spark eroding, burning, die sinking or wire erosion, is a manufacturing process whereby a desired shape is obtained using electrical discharges (sparks). In the present day of technological advancement in industries like, automobile, aeronautics, nuclear, mould, tools and die making industries, there is a heavy demand of the advanced materials with high strength, high hardness, temperature resistance and high strength to weight ratio etc. This necessity leads to evolution of advance materials like high strength alloys, ceramics, fiber-reinforced composites etc. In machining of these materials, conventional manufacturing processes are increasingly being replaced by more advanced techniques, which use different form of energy to remove the material because these advance materials are difficult to machine by the conventional machining processes, and it is difficult to attain good surface finish with close tolerance. Electrical discharge machining is a machining method primarily used for hard metals or those that would be very difficult to machine with

traditional techniques. EDM typically works with materials that are electrically conductive, although methods for machining insulating ceramics with EDM have also been proposed. EDM can cut intricate contours or cavities in pre-hardened steel without the need for heat treatment to soften and re-harden them. Also, applications of this process to shape polycrystalline diamond tools have been reported. To obtain a specific geometry, the EDM tool is guided along the desired path very close to the work; ideally it should not touch the workpiece, although in reality this may happen due to the performance of the specific motion control in use. In this way, a large number of current discharges (colloquially also called sparks) happen, each contributing to the removal of material from both tool and workpiece, where small craters are formed. The size of the craters is a function of the technological parameters set for the specific job at hand. The presence of these small craters on the tool results in the gradual erosion of the electrode. In the present study the optimal condition of MRR has been evaluated with the correlation of machining parameters like discharge current, pulse on time, pulse off time. The objective of this research

\*Corresponding Author: Department of Production and Industrial Engineering, Delhi Technological University, New Delhi, India (E-mail: ranganathdce@gmail.com)

\*\*Department of Production and Industrial Engineering, Delhi Technological University, New Delhi, India


\*\*\*Department of Mechanical Engineering, Kasturba Polytechnic, New Delhi, India

\*\*\*\*Department of Electrical Engineering, IMSEC, Ghaziabad, Uttar Pradesh, India

work is to study MRR and surface roughness with the following design variables:

1. Discharge current
2. Pulse on Time (Ton)
3. Pulse off Time (Toff)

**Fig 1: Full Factorial Design (27 Points)**

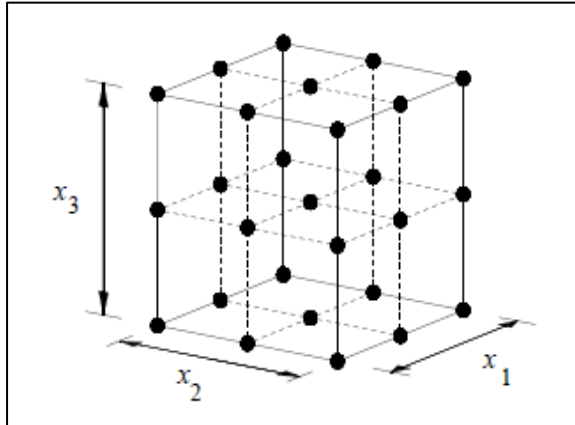

Montgomery in 1997 given a full factorial approach to construct an approximation model. A *factorial* experiment is an experimental strategy in which design variables are varied together, instead of one at a time. The lower and upper bounds of each of  $N$  design variables in the optimization problem needs to be defined. The allowable range is then discretized at different levels. If each of the variables is defined at only the lower and upper bounds (two levels), the experimental design is called  $2^N$  full factorial. Similarly, if the midpoints are included, the design is called  $3^N$  full factorial and shown in Figure.

Generally, for a large number of variables, the number of experiments grows exponentially ( $3^N$  for a full factorial) and becomes impractical. A full factorial design typically is used for five or fewer variables.

The experiments were conducted on the machining of EN 31 die steel with graphite electrode with electrical discharge machining (EDM). The EDM oil commercial grade has been used as dielectric fluid. The effect of various EDM parameters such as discharge current, Ton and Toff has been investigated to yield the response in terms of MRR. In this work mathematical models have been developed for relating the MRR with machining parameters like discharge current, Ton, and Toff. The

optimum value has been determined with the help of main effect plot and ANOVA table.

## 2.0 Experimental Setup

The experiments for the have been conducted on Spark erosion machine (SPARKMAN SN-35, Sparkonix) as shown in Fig.1. The machine has maximum current capacity of 35 amps. The experiment was conducted in straight polarity i.e. the tool was connected to the negative terminal whereas workpiece was connected to the positive terminal. In the present study the optimal condition of MRR has been evaluated with the correlation of machining parameters like discharge current, pulse on time, pulse off time. The machining conditions used during experimentation have been shown in table1. Work piece material was cut into rectangular cross section and top and bottom faces of the work piece were ground to make flat and good surface finish prior to experimentation. A photograph of the EDMed work piece is shown in fig 2. The graphite electrode of diameter  $\phi 35\text{mm}$  is used with EDM oil as dielectric. Machining depth was kept constant at 1mm for every experimental run and corresponding machining time was measured. After each run the work piece was removed from the machine, dried and weighed before and after machining.

**Fig 2: EDM machine SPARKMAN SN-35, Sparkonix**



### 3.0 Results and Discussions

There are large numbers of factors to be considered for MRR calculation in EDM process but in the present work discharge current, pulse on time (Ton), and pulse off time (Toff) have only been taken into account as design factors. The reason why these three factors have been selected as design factors is that they are the most widespread and used amongst EDM researchers. Material removal rate was calculated from the difference of weight of work piece before and after machining process.  $MRR = (W_i - W_f) / T$  gm/min, Where  $W_i$  is the initial weight and  $W_f$  is the final weight after machining and  $T$  is the total time taken for the machining.

**Fig 3: Photograph of EDMed Work Piece**



**Table 1: Machining Condition used During Experimentation**

Electrode	Work piece	Dielectric Fluid	Flushing Type
Graphite, $\phi 35$ mm Thermal conductivity 80 W/m-k Melting point 4800 °C Electrical resistivity $3.5 \times 10^{-3}$ ohm-cm Specific heat capacity 7.10 J/g °C	EN 31 die steel Elements Composition (wt. %) C 1.07 Si 0.32 Mn 0.58 P 0.04 S 0.03 Cr 1.12 V - Fe Balance	EDM Oil Specific Gravity 0.757 Flash Point 108°C Pour Point 0°C, Viscosity cSt @40°C 3.05 Copper Corrosion 1A Dielectric Strength 40	Submerged

**Table 2: Values of Variables at Different Level**

Factors		LEVELS	
-1	0	+1	UNIT
Control factors	I	II	III
Discharge current	8	10	12
Pulse duration(TON)	4	6	8
			Micro second

### 4.0 Results and Analysis of MRR

#### ANOVA (Analysis of Variance)

The purpose of the statistical analysis of variance (ANOVA) is to investigate which design parameter significantly affects the material removal rate.

Based on the ANOVA, the relative importance of the machining parameters with respect to material removal rate is investigated to determine more accurately the optimum combination of the machining parameters.

**Table 3: ANOVA: MRR (gm/min) versus Current, Ton, Toff**

Factor	Type	Levels	Values
Current	random	3	8, 10, 12
Ton	Fixed	3	4, 6, 8
Toff	Fixed	3	3, 5, 7

**Table 4: Analysis of Variance for MRR (gm/min)**

Source	DF	SS	MS	F	P
Current	2	0.042855	0.021428	7.19	0.004
Ton	2	0.028876	0.014438	4.84	0.019
Toff	2	0.002804	0.001402	0.47	0.632
Error	20	0.059619	0.002981		
Total	26		0.134155		

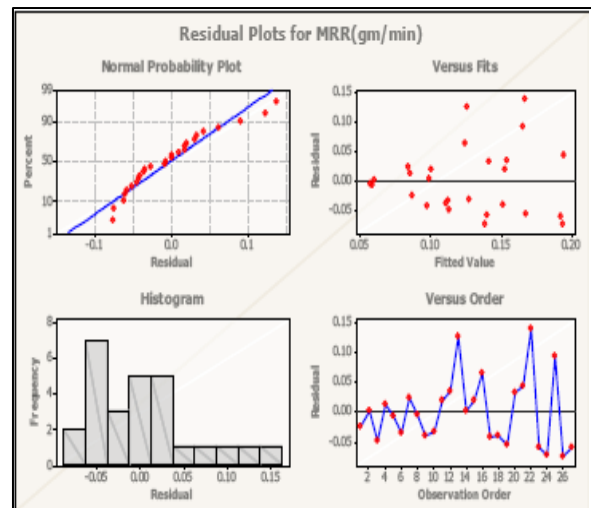
$S = 0.0545981$   $R\text{-Sq} = 55.56\%$   $R\text{-Sq}(\text{adj}) = 42.23\%$

**Table 5: Experimental Results and S/N Ratis of MRR**

Exp No	Peak Current	T ON	TO FF	Initial Wt(g m)	Final Wt(g m)	Time taken(min)	MRR(g m/min)
1	8	6	7	565.365	554.253	184	0.0604
2	10	6	7	565.363	558.063	117	0.0624
3	12	6	7	561.131	553.632	78	0.0961
4	8	8	7	599.231	591.921	146	0.05
5	10	8	7	595.912	588.531	97	0.0761
6	12	8	7	530.501	522.481	76	0.1055
7	8	4	7	470.015	464.164	117	0.05
8	10	4	7	465.392	458.911	92	0.0704
9	12	4	7	433.981	426.951	76	0.0925
10	8	6	5	464.162	458.081	51	0.1192
11	10	6	5	458.915	452.531	34	0.1878
12	12	6	5	522.092	516.821	21	0.251
13	8	8	5	570.441	563.43	70	0.1001
14	10	8	5	514.771	507.581	42	0.1712
15	12	8	5	532.352	525.221	38	0.1877
16	8	4	5	533.423	527.812	105	0.0534
17	10	4	5	491.572	486.642	45	0.1096
18	12	4	5	524.014	518.073	54	0.11
19	8	6	3	527.815	520.384	43	0.1728
20	10	6	3	486.642	479.513	30	0.2376
21	12	6	3	442.132	435.121	23	0.3048
22	8	8	3	463.075	456.714	80	0.0795
23	10	8	3	459.915	453.065	58	0.1181
24	12	8	3	435.101	427.391	30	0.257
25	8	4	3	456.712	450.292	104	0.0617
26	10	4	3	453.064	446.945	47	0.1302
27	12	4	3	438.981	433.982	26	0.1922

The regression equation is

$$\text{MRR(gm/min)} = 0.0203 \text{ Current} - 0.0134 \text{ Ton} + 0.00063 \text{ Toff}$$

**Fig 4: Residual Plots for MRR**

## 5.0 Conclusions

After analyzing the results of the experiment performed on EN31 die steel with graphite electrode material with different discharge current, Ton and Toff, following conclusions are arrived at:

MRR increases with increase in discharge current. The enhancement in MRR may be attributed due to increase in pulse energy as the current increases. At higher levels of current, wear rate of graphite increases and causes some machining problems which further reduces MRR. This may be due to arc produced at high current densities. With increase in Ton for same discharge current the MRR decreases. With increase in Toff for the same current the MRR decreases. With lower Toff the MRR is more as compared to lower Ton.

## References

- [1] A Medfai, M. Boujelbene, E. Bayraktar, A mathematical model to choose effective cutting parameters in electro-erosion, EDM, Journal of Achievements in Materials and Manufacturing Engineering, 47(1), 2003, 97-102

- [2] M. Boujelbene, E. Bayraktar, W. Tebni, S. B. Salem, Influence of machining parameters on the surface integrity in electrical discharge machining, *Archive of Materials science and Engineering*, 37(2), 2009, 110-116
- [3] A. K. M. A. Iqbal, A. A. Khan, Influence of Process Parameters on Electrical Discharge Machined Job Surface Integrity, *American J. of Engineering and Applied Sciences*, 3(2), 2010, 396-402
- [4] A. K. Khanra, L.C. Pathak, M. M. Godkhindi, Microanalysis of debris formed during electrical discharge machining (EDM), *Journal of Materials Science*, 42, 2007, 872-877
- [5] H. T. Lee, T. Y. Tai, Relationship between EDM parameters and surface crack formation, *Journal of Materials Processing Technology*, 142, 2003, 676-683
- [6] C. J. Luis, I. Puertas, G. Villa, Material removal rate and electrode wear study on EDM of silicon carbide, *J Mater Process Technol*, 164/165, 2005, 889-896
- [7] M. Kunieda, B. Lauwers, K. P. Rajurkar, B. M. Schumacher, *Advancing EDM through Fundamental Insight into the Process*, 2006
- [8] M. Mahardika, K. Mitsui, A new method for monitoring microelectric discharge machining processes, *International Journal of Machine Tools and Manufacture*, 48, 2008, 446-458
- [9] R. A. Mahdavi, EDM process optimisation via predicting a controller model, *Archives of computational materials science and surface engineering*, 1(3), 2009, 161-167
- [10] M. K. Pradhan, C. K. Biswas, Modelling of achieving parameters for MRR in EDM using response surface methodology, *National Conference on Mechanism Science and Technology*, 13-14, 2008, 535-542
- [11] H. S. Payal, Analysis of electrical discharge machined surfaces of EN-31 tool steel, *Journal of scientific and industrial research*, 67, 2008, 1072-1077
- [12] G. P. Petropoulos, Multi-parameter analysis and modeling of engineering surface texture, *Journal of Achievements in Materials and Manufacturing Engineering*, 24, 2007, 91-100
- [13] I. Puertas, C. J. Luis, A study on the machining parameters optimisation of electrical discharge machining, *Journal of Materials Processing Technology*, 143-144, 2003, 521-526
- [14] R. Choudhary, H Kumar, R K Garg, Analysis and evaluation of heat affected zones in electric discharge machining of EN-31 die steel, *Indian Journal of Engineering & Materials Sciences*, 17, 2010, 91-98
- [15] Ranganath M. S., Vipin, Experimental Investigation and Parametric Analysis of Surface Roughness in CNC Turning Using Design of Experiment" *International Journal of Modern Engineering Research*, 4(9), 2014
- [16] Ranganath M S, Vipin, Harshit, Surface Finish Monitoring in CNC Turning Using Response Surface Methodology: A Review, *International Journal of Emerging Technology and Advanced Engineering*, , 4(10), 2014
- [17] Ranganath M S, Vipin, Nand Kumar, R. Srivastava, Surface Finish Monitoring in CNC Turning Using RSM and Taguchi Techniques, *International Journal of Emerging Technology and Advanced Engineering*, 4(9), 2014, 171-179
- [18] S. S. Baraskar, S. S. Banwait, S. C. Laroia, *Mathematical Modeling of Electrical Discharge Machining Process through*

- Response Surface Methodology, International Journal of Scientific & Engineering Research, 2(11), , 2011, 1-10
- [19] Vipin, B.B Arora, J. Kumar, Analysis of Metal Removal Rate in EDM Process, International Journal of Engineering and Manufacturing Science, 1(3), 2010, 101-107
- [20] Vipin, H. Kumar, Surface Roughness Prediction Model by Design of Experiments For Turning Leaded Gun Metal, International Journal of Applied Engineering Research, 4(12), 2009, 2621–2628