

Article Info

Received: 25 Jan 2017 | Revised Submission: 20 Feb 2017 | Accepted: 28 Feb 2017 | Available Online: 15 Jun 2017

Surface Integrity, Surface Finish and Corrosion Characteristics of Stainless Steels in Saline Water Medium

Abhimanyu Chaudhari*, Ankur Srivastava**, Tushar K Roy***, Ajit K Chakrabarti**** and MN Dastur*****

ABSTRACT

The surface roughness of austenitic (304), martensitic (410) and ferritic (430) grades of stainless steels have been measured after fine emery paper grinding. The surface integrity of the ground samples were further examined in SEM. Metal removal during emery paper grinding occurred by rubbing, ploughing, micro cracking and gouging out of metal grains. The rate of corrosion/year, as determined through potentiostat test in 0.9 N NaCl solution, increased with surface roughness but it was insignificant in case of the metallographically polished samples of all the stainless steels. Corrosion progressed fast from the grinding pits on the stainless steel sample surfaces.

Keywords: Stainless Steel; Rubbing; Ploughing; Micro cracking.

1.0 Introduction

Stainless steels are often used in corrosive environments. Although stainless steels are resistant to attack of oxidizing acids, most of the stainless steel grades are amenable to corrosion in saline medium [1], surface finish of the steels influence resistant to corrosion [2]. The austenitic stainless steel 304L is widely used as a structural material for which surface finish has signification effect on the service performance. A reference for choosing appropriate grinding parameters for machining 304L stainless steel has been provided by Nian Zhou, et al [3]. Another study also indicated that the surface roughness of the workpiece material is largely affected by the machining method and the parameters used [4]. The potentiostat technique has been used in the past to examine the overall corrosion behaviour of 316SS [5]. Similarly corrosion resistance behaviour of S43903 ferritic stainless steel was evaluated in

different hydrochloric acid solution and the acid chloride concentration [6]. Surface integrity has a significant effect on service condition and residual stress may influence failure of duplex stainless steels in service [7].

Table 1: Chemical Composition of Stainless Steels Samples.

Table: 1(a) Austenetic(304)

Carbon	0.08
Manganese	1.36
Phosphorus	0.03
Sulphur	0.03
Silicon	0.6
Aluminium	trace
Chromium	19.05
Nickel	9.73
Iron	balance

*Corresponding Author: School of Materials Science and Engineering, Indian Institute of Engineering Science and Technology, Shibpur, Howrah -711103, (W Bengal) India (E-mail: akc1940@gmail.com)

**School of Materials Science and Engineering, Indian Institute of Engineering Science and Technology, Shibpur, Howrah -711103, (W Bengal) India

***School of Materials Science and Engineering, Indian Institute of Engineering Science and Technology, Shibpur, Howrah -711103, (W Bengal) India

****School of Materials Science and Engineering, Indian Institute of Engineering Science and Technology, Shibpur, Howrah -711103, (W Bengal) India

*****School of Materials Science and Engineering, Indian Institute of Engineering Science and Technology, Shibpur, Howrah -711103, (W Bengal) India

Table: 1(b) Martensitic (410)

Carbon	0.15
Manganese	1.36
Phosphorus	0.04
Sulphur	0.04
Silicon	0.5
Aluminium	trace
Chromium	12.72
Nickel	trace
Iron	balance

Table: 1(c) Ferritic(430)


Carbon	0.11
Manganese	1.31
Phosphorus	0.04
Sulphur	0.04
Silicon	0.65
Aluminium	trace
Chromium	18.19
Nickel	trace
Iron	balance

Table 2: Electrochemical Data Extracted from Polarization Curves for three Different Grades of Stainless Steels in 0.9n NaCl Solution at Room Temperature.


Steel Type	ECorr (mV)	ICorr ($\mu\text{A}/\text{cm}^2$)	Corrosion Rate ($\mu\text{m}/\text{year}$)
304SS Emery paper grinding	-604.1	5.3424	61.894
304SS Polished Sample	-266.6	0.0176	0.20384
410SS Emery paper grinding	-479.2	3.9988	46.327
410SS Polished Sample	-369.6	2.5595	29.658
430SS Emery paper grinding	-651.3	12.6131	146.12
430SS Polished Sample	-177.2	0.2536	2.9383

Fig 1: Microstructure of as Received Stainless Steel Samples


(a) Austenitic 304

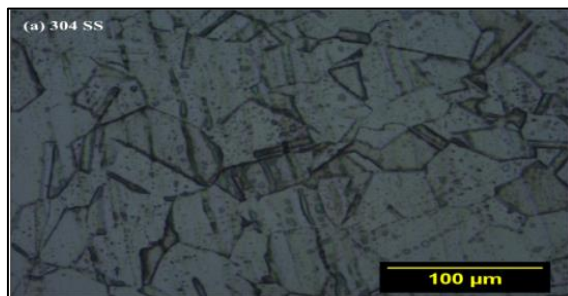

(b) Martensitic 410

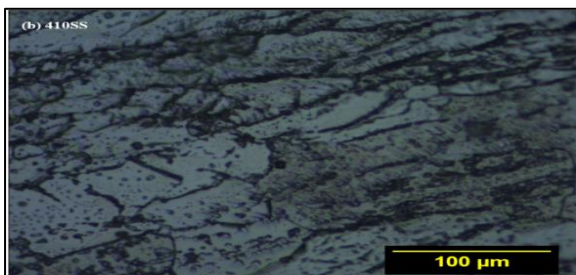

(c) Ferritic 430

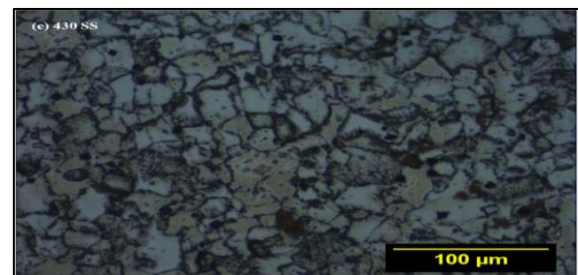

In this study the specific effect of emery paper polishing on the surface integrity and surface finish of austenitic (304), martensitic (410) and ferritic (430) stainless steels and its ultimate effect on corrosion characteristics in 0.9N NaCl solution has been examined.

2.0 Experimental Procedure

The composition of the as received 5mm thick stainless steels plates are given in table 1. The microstructures of steels are shown in fig.1 (a, b & c).

The plates were polished by emery paper grinding. The emery papers were coated with silicon carbide (SiC) abrasive particles of grit size 240#. The surface roughness of the emery paper ground samples were measured by a Bruker Contour Elite K 3D optical surface profilometer.

In the current work, three area of each ground samples were measured and the reported roughness is the average of these three measurements.

For the purpose of comparison, the surface roughness of metallographically polished samples of the three steels was also measured.

The surface characteristics of the ground samples were examined by scanning electron microscopy (Hitachi S-3400M).

Corrosion characteristics of both the ground and metallographically polished samples of the three stainless steels were determined by potentiostat test.

Each square shape test sample had a surface area of $1\text{cm} \times 1.5\text{cm}$.

Each experiment was conducted in 100ml of 0.9N NaCl solution.

From each area ($1.26\text{mm} \times 0.9\text{mm}$) of measurement, roughness values and R_a were calculated.

The R_a value is the arithmetic average value of the roughness profile determined from deviations about the mean line over the evaluation length.

Fig: 2. Surface Finish Data are Presented in Bar Diagram form

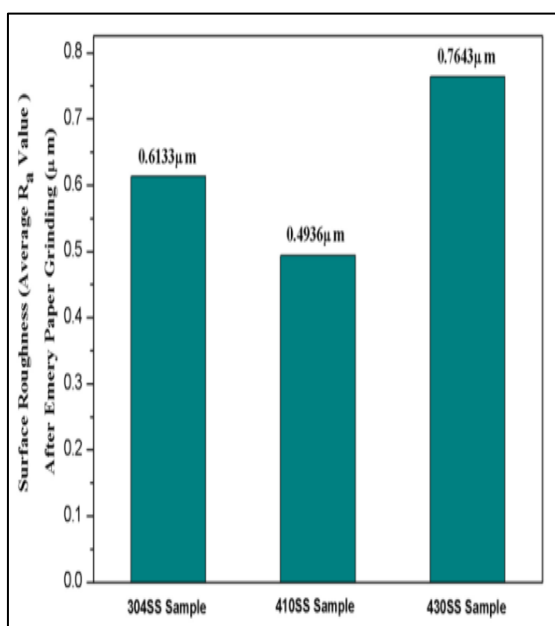


Fig 3(a): 3D Pictures of the Surface Topography and Surface Roughness of 304 Stainless Steel Sample obtained after Emery Paper Grinding by 3d Optical Surface Profilometer

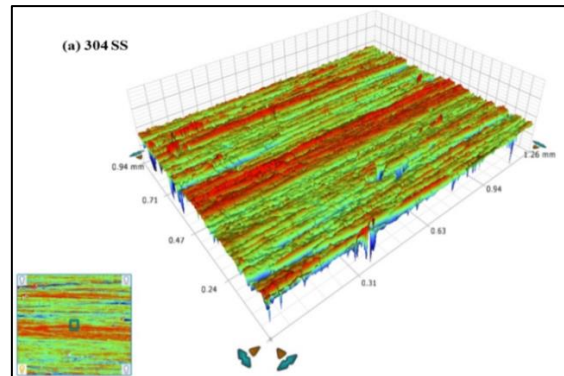


Fig: 3(b). 3D Pictures of the Surface Topography and Surface Roughness of 410 Stainless Steel Sample obtained after Emery Paper Grinding by 3d Optical Surface Profilometer

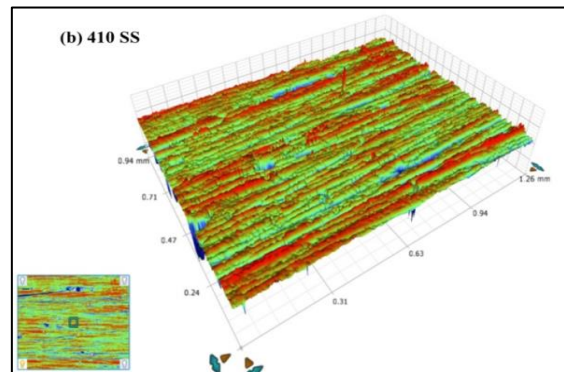


Fig: 3(c). 3D Pictures of the Surface Topography and Surface Roughness of 430 Stainless Steel Sample obtained after Emery Paper Grinding by 3d Optical Surface Profilometer

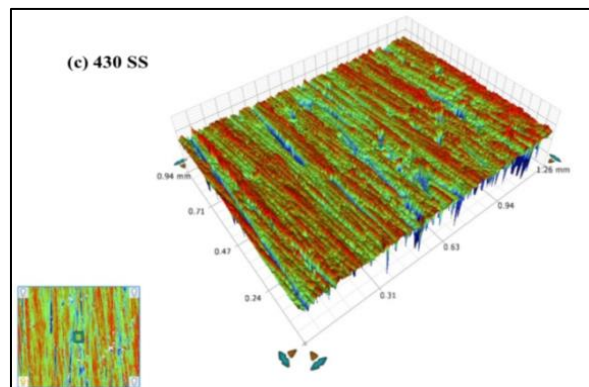


Fig 4(a): 304 Stainless Steel Sample Sem Photographs Ofemery Paper Grinding

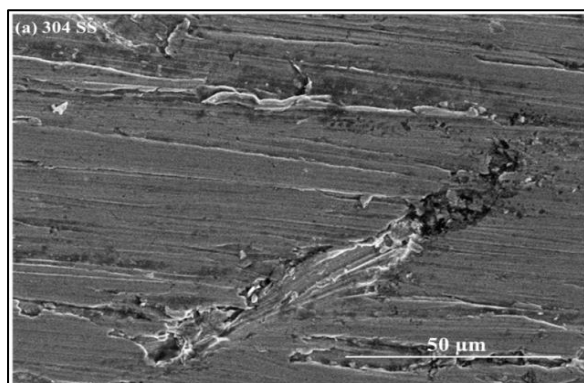


Fig 5(a): The experimental Polarisation Curve of 304 Stainless Steel Sample

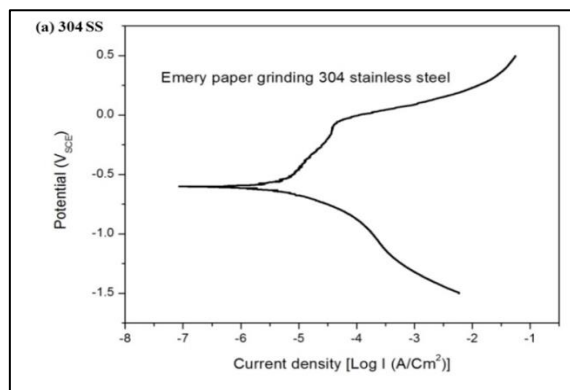


Fig 4(b): 410 Stainless Steel Sample Sem Photographs Ofemery Paper Grinding

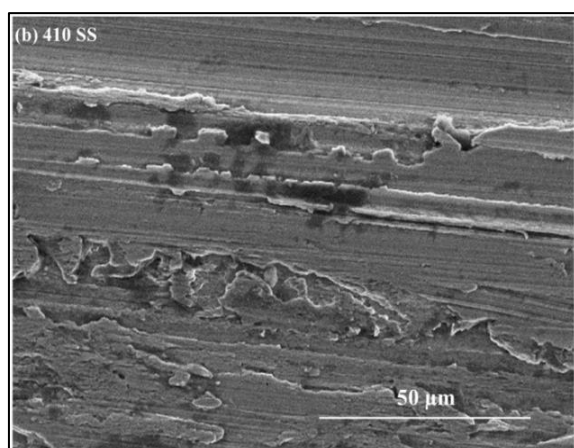


Fig 5(b): The Experimental Polarisation Curve of 410 Stainless Steel Sample

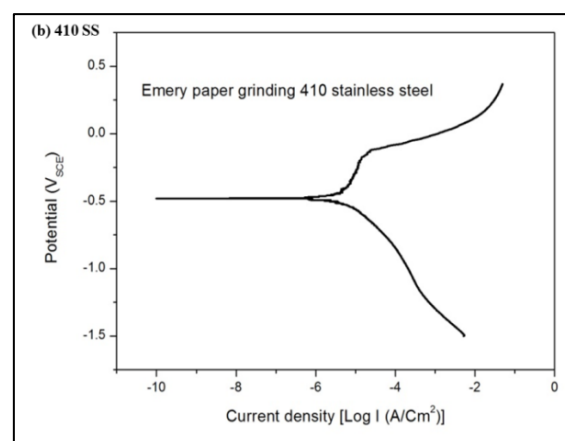


Fig 4(c): 430 Stainless Steel Sample Sem Photographs Ofemery Paper Grinding

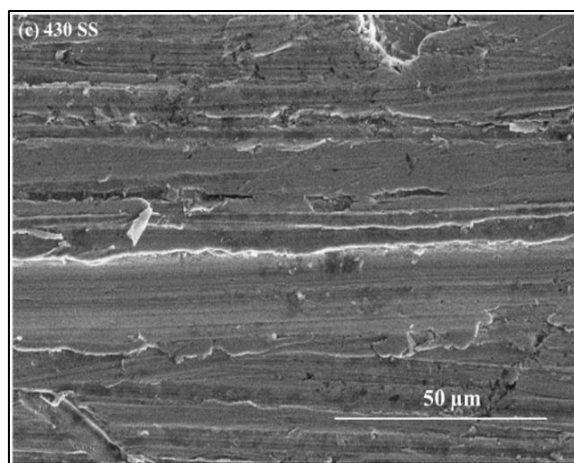


Fig 5(c): The Experimental Polarisation Curve of 430 Stainless Steel Sample

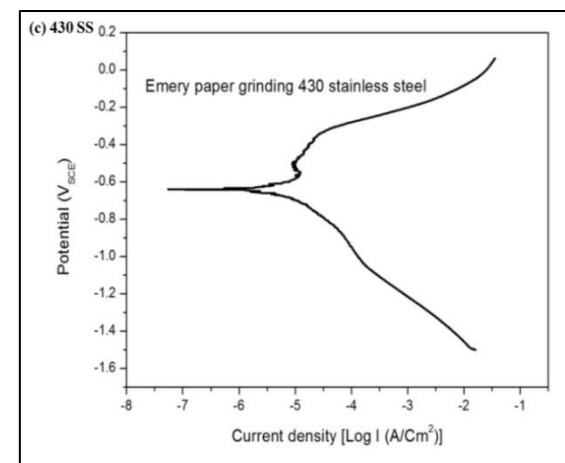


Fig 6(a): Emery Paper Grinding Corroded Sample of 304 Stainless Steel Sample

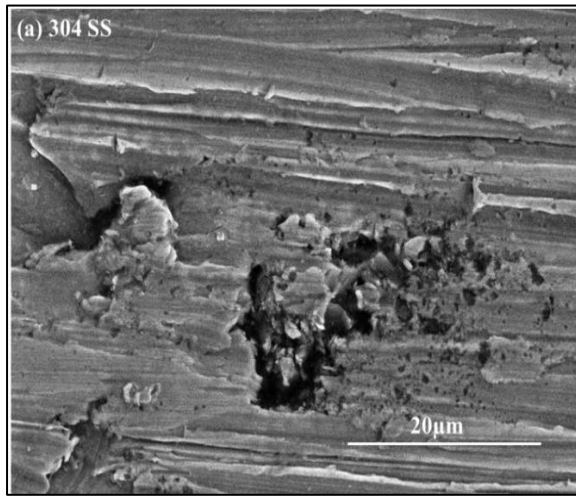


Fig 6(b): Emery Paper Grinding Corroded Sample of 410 Stainless Steel Sample


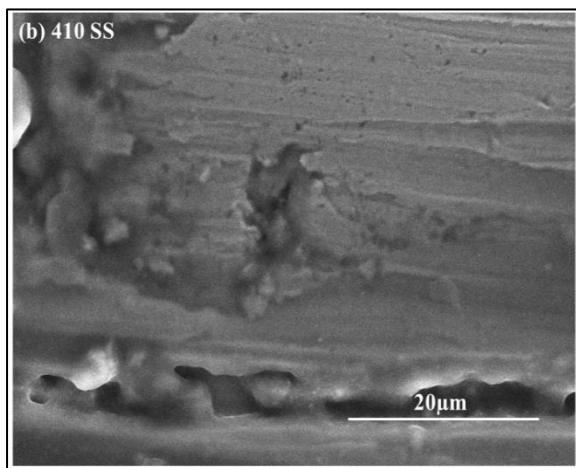


Fig 6(c): Emery Paper Grinding Corroded Sample of 430 Stainless Steel Sample

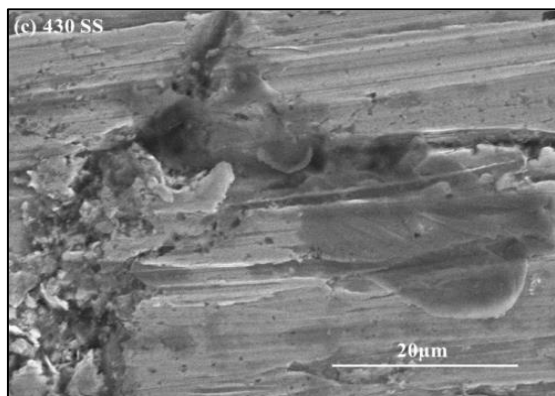

3.0 Result and Discussion

The surface finish data are presented in bar diagram form in fig.2. The 410 martensitic stainless steel developed the smoothest surface, obviously because of its higher hardness.

The ferritic 430 stainless steel had developed the roughest surface. Of course, the variation of roughness of all the steels was in the range of 0.5 to 0.75 μm only. Comparatively, the roughness of the metallographically polished samples was insignificant. The mode of metal removal and the extent of surface damage could be better appreciated from the 3D pictures and SEM photographs of the surfaces presented in fig.3 (a, b & c) and fig.4 (a, b & c).

Emery paper grinding progressed mainly by rubbing and ploughing. But it is apparent from the SEM photographs in fig.4 (a, b & c) that microcracking and gouging out of grains also occurred.

The gouging effect was most prominent in case of 304 stainless steel, which was the softest steel among the three.

The electrochemical data collected from the potentiostat test are presented in table 2. The potentiostat curves are presented in fig.5 (a, b & c). The tabular data clearly illustrate the effect of surface finish. The metallographically polished samples of the three steels suffered insignificant corrosion compared to that of the emery paper ground samples. The corrosion rate/year was highest for the 410 stainless steel, and lowest for the 430 stainless steel, which recorded maximum and minimum roughness respectively after emery paper grinding.

The SEM photographs of the corroded samples of the three stainless steels shows corrosion pits in fig.6 (a, b & c). Figure 6 (a) shows corrosion pits are most prominently formed in region of grains pull outs. The ploughing marks are still present. In addition to the formation of corrosion pits, the cracks on the surface have also suffered further corrosion in case of 410 stainless steel sample shown in figure 6 (b). The corrosion pattern on 430 stainless steel surface shown in figure 6 (c) is more or same as in figure 6 (b). Surface finish is known to have marked effect on pitting corrosion.

The present results are in conformity with the existing epicene that pitting corrosion is less likely to occur on a polished than on the ground surfaces.

4.0 Conclusions

- Metal removals from surfaces of different grades of stainless steels occur by rubbing, ploughing and gouging out of grains. Surface roughness of all types of stainless steels after the emery paper grinding is still significantly high.
- Surface roughness has direct influence on the corrosion rate of stainless steels in 0.9N NaCl solution.
- Corrosion progresses prominently from the pits generated during emery paper grinding.

Acknowledgment

The authors wish to thank the Dr. MN Dastur, School of Materials Science and Engineering for provision of laboratory facilities for the work. They are also thankful to Associate Prof. Debdulal Das, Assistant Prof. S.Kundu, Dr. Malay Kundu and ShriSudip Bhattacharjee of IEST Shibpur for their help in various steps of the work.

- i. Abhimanyu Chaudhari is the principal investigator and principal author.
- ii. Ankur Srivastava helped him in specimen preparation and collection of reprints.
- iii. Prof. Ajit K. Chakrabarti is the principal supervisor for Mr. Abhimanyu Chaudhari.
- iv. Prof. Tushar K. Roy is co-supervisor for Abhimanyu Chaudhari.

References

- [1.] Outokumpu. Corrosion and corrosion properties, Handbook of Stainless Steel, Riihitontuntie, Finland, 2013, 34-44
- [2.] MG Fontana. Corrosion Engineering, Tata McGraw Hill, New Delhi, India, 3rd Edition, 2005, 77

- [3.] N Zhou, R Pettersson, RL Peng, M Schöning. Effect of surface grinding on chloride induced SCC of 304L. Materials Science and Engineering. A, 658, 2016, 50-59.
- [4.] P Junlabuddee, C Saikaew.. A Study on factor affecting surface roughness in turning process of AISI 316L stainless steel by Shainin design of experiment method. KKU Engineering Journal, 42(1), 2015, 71-81.
- [5.] CA Loto, RT Loto. Electrochemical Corrosion Resistance Evaluation of Ferritic Stainless Steel in HCl. International Journal of Electrochemical Science, 7, 2012, 11011-11022.
- [6.] ST Arab, MI Abdulsalam, HM Alghamdi, KM Emran, (2014). The Crevice Corrosion of 316L SS Alloy in NaCl Solution at Different Applied Potentials. Open Journal of Physical Chemistry, 2014
- [7.] N Zhou, RL Peng, R Pettersson. Surface integrity of 2304 duplex stainless steel after different grinding operations. Journal of Materials Processing Technology, 229, 2016, 294-304.

Nomenclature

SEM	Scanning Electron Microscope
SS	Stainless Steel
Ra	Arithmetic average roughness
µm	micrometer
E _{Corr}	Potential corresponding to active to passive zone
I _{Corr}	Current density for passive layer formation